



**University of Belgrade
Technical Faculty in Bor**



**Chamber of Commerce
and Industry of Serbia**

XV International Mineral Processing & Recycling Conference



INTERNATIONAL MINERAL PROCESSING & RECYCLING CONFERENCE

Proceedings

Editors:
Jovica Sokolović
Milan Trumić

**17-19 May
2023**

**Belgrade
SERBIA**



**University of Belgrade,
Technical faculty in Bor**

**Chamber of Commerce
and Industry of Serbia**

XV International Mineral Processing & Recycling Conference



Proceedings

**Editors:
Jovica Sokolović
Milan Trumić**

17 – 19 May 2023, Belgrade, Serbia

XV International Mineral Processing & Recycling Conference

PUBLISHER:

University of Belgrade, Technical Faculty in Bor

FOR THE PUBLISHER:

Dean: Prof. Dr Dejan Tanikić

EDITORS:

Prof. Dr Jovica Sokolović

Prof. Dr Milan Trumić

PROCEEDINGS COVER DESIGN:

Vojislav Jotović

PRINTED BY:

Grafomed - Trade Bor d.o.o., Bor, Serbia

Printed: 200 copies

PUBLICATION YEAR:

2023

=====
CIP - Каталогизacija у публикацији
Народна библиотека Србије, Београд

622.7(082)
502.131.1:628.477.6(082)
628.477.6(082)

INTERNATIONAL Mineral Processing and Recycling Conference (15 ; 2023 ; Belgrade)
Proceedings / XV International Mineral Processing and Recycling Conference, IMPRC, 17-19
May 2023, Belgrade, Serbia ; editors Jovica Sokolović, Milan Trumić. - Belgrade : University,
Technical Faculty in Bor, 2023 (Bor : Grafomed Trade). - XII, 634 str. : ilustr. ; 25 cm

Na vrhu nasl. str.: Chamber of Commerce and Industry of Serbia. - Tiraž 200. - Bibliografija uz
većinu radova.

ISBN 978-86-6305-133-1

а) Руде -- Припрема -- Зборници б) Отпадне материје -- Одрживи развој -- Зборници в)
Отпадне материје -- Рециклажа -- Зборници

COBISS.SR-ID 114566153

=====



***Conference is financially supported
by Republic of Serbia,
Ministry of Science, Technological Development
and Innovation***

COMMITTEES

Scientific Committee

Prof. Dr Milan Trumić, Serbia, President;
Prof. Dr Grozdanka Bogdanović, Serbia, Vice President;
Prof. Dr Jovica Sokolović, Serbia, Vice President;
Prof. Dr Zhiyong Gao, China;
Prof. Dr Lijie Guo, China;
Prof. Dr Mauricio Torem, Brazil;
Prof. Dr Pablo Brito-Parada, United Kingdom;
Prof. Dr Przemyslaw Kowalczyk, Norway;
Prof. Dr Erin Bobicki, Canada;
Prof. Dr Kazutoshi Haga, Japan;
Dr Maoming Fan, USA;
Dr Aleksandar Janković, Australia;
Prof. Dr Rraghupatruni Bhima Rao, India;
Prof. Dr Junbeum Kim, France;
Prof. Dr Srećko Stopić, Germany;
Prof. Dr Magdalena Regel-Rosocka, Poland;
Prof. Dr Alejandro Rodriguez Pascual, Spain;
Prof. Dr Georgios Anastassakis, Greece;
Prof. Dr Mehmet Polat, Turkey;
Prof. Dr Valery Morozov, Russian Federation;
Prof. Dr Silvie Heviánková, Czech Republic;
Dr Slavomir Hredzak, Slovakia;
Prof. Dr Gabor Musci, Hungary;
Prof. Dr Francisc Popescu, Romania;
Prof. Dr Irena Grigorova, Bulgaria;
Prof. Dr Jakob Lamut, Slovenia;
Prof. Dr Aleksandra Anić Vučinić, Croatia;
Prof. Dr Ilhan Bušatlić, Bosnia & Herzegovina;
Prof. Dr Svjetlana Sredić, Bosnia & Herzegovina;
Prof. Dr Mirjana Golomeova, North Macedonia;
Prof. Dr Aleksandar Jovović, Serbia;
Prof. Dr Milena Kostović, Serbia;
Prof. Dr Željko Kamberović, Serbia;
Prof. Dr Vlada Veljković, Serbia;
Prof. Dr Goran Vujić, Serbia;
Prof. Dr Srđan Rončević, Novi Sad, Serbia;
Prof. Dr Bogdana Vujić, Serbia;

Prof. Dr Marina Stamenović, Serbia;
Prof. Dr Nada Štrbac, Serbia;
Prof. Dr Milan Antonijević, Serbia;
Prof. Dr Zoran Stević, Serbia;
Prof. Dr Dejan Tanikić, Serbia;
Prof. Dr Snežana Šerbula, Serbia;
Prof. Dr Snežana Milić, Serbia;
Prof. Dr Mira Cocić, Serbia;
Prof. Dr Zoran Štirbanović, Serbia;
Prof. Dr Maja Trumić, Serbia;
Prof. Dr Ljubiša Andrić, Serbia;
Asst. Prof. Dr Vladan Milošević, Serbia;
Dr Ivana Smičklas, Serbia;
Dr Miroslav Sokić, Serbia;
Dr Dragan Radulović, Serbia;
Dr Sonja Milićević, Serbia;
Dr Milinko Radosavljević, Serbia;
Dr Mile Bugarin, Serbia;
Dr Zoran Stevanović, Serbia;
Dr Radmila Marković, Serbia;
Dr Miroslav Ignjatović, Serbia.

Organizing Committee

Prof. Dr Jovica Sokolović, President, Serbia;
Prof. Dr Milan Trumić, Serbia;
Prof. Dr Grozdanka Bogdanović, Serbia;
Prof. Dr Zoran Stević, Serbia;
Prof. Dr Zoran Štirbanović, Serbia;
Prof. Dr Maja Trumić, Serbia;
Dr Miroslav Ignjatović, Serbia;
Dr Vladimir Nikolić, Serbia;
MSc Dragana Marilović, Serbia;
MSc Predrag Stolić, Serbia;
MSc Katarina Balanović, Serbia;
MSc Ivana Ilić, Serbia;
MSc Oliver Marković, Serbia;
BSc Vera Ražnatović, Serbia;
BSc Sandra Vasković, Serbia;
Dobrinka Trujić, Serbia.

TABLE OF CONTENTS

PLENARY LECTURES	1
L. Guo, Y. Zhao, Q. Ma, G. Tang, C. Jia, C. Li RESEARCH PROGRESS, TRENDS, AND INNOVATIONS OF DEVELOPMENT ON MINING BACKFILL TECHNOLOGY OF UNDERGROUND METALLIFEROUS MINE	3
V.A. Chanturia, V.V. Morozov, G.P. Dvoichenkova, E.L. Chanturia, Yu. A. Podkamenny INNOVATIVE TECHNOLOGY FOR THE RECOVERY OF ABNORMALLY LUMINESCENT DIAMONDS BASED ON THE USE OF LUMINOPHORE-CONTAINING MODIFIERS	23
G. Vujić N. Maoduš, M. Živančev WTE AS INTEGRATED PART OF CIRCULAR ECONOMY	32
J.C. Gabriel, H. Bo, N. Charpentier, S. Chevrier, Y. Deng, F.Olivier, D. Xia CRITICAL METALS RECOVERY FROM E-WASTE: FROM MICROFLUIDICS HYDROMETALLURGY TO ECONOMICALLY VIABLE PROCESSES	39
SESSION LECTURES	41
F. Nakhaei, I. Jovanović 3D IMAGING AND APPLICATIONS IN MINERAL PROCESSING	43
D. Singh, S. Basu, B. Mishra. R. Bhima Rao NOVEL APPROACHES TO RECOVER TOTAL HEAVY MINERALS FROM DIFFERENT GRADE BEACH SAND DEPOSITS USING GRAVITY CONCENTRATORS	54
M. Trumić, K. Balanović ROLE OF PARTICLE SHAPE IN THE FLOATABILITY OF TONER PARTICLE	64
I. Smičiklas, M. Egerić, M. Jović COPPER SORPTION CAPACITY OF THE SOIL TREATED WITH UNCONVENTIONAL ALKALIZING AGENTS	73
V. Conić, I. Jovanović COPPER ORE BIOLEACHING FROM ECOLOGICAL POINT OF VIEW	79
S. Cvetković, M. Popović, J. Perendija LIFE CYCLE ASSESSMENT AND USE OF NATURAL RESOURCES	89
WORKSHOP PAPERS	95
P. M. Angelopoulos, G. Anastassakis, N. Kountouris, N. Koukoulis, M. Taxiarchou COMBINED USE OF ORGANOSOLV LIGNIN AND XANTHATES ON SPHALERITE FLOTATION FROM MIXED SULPHIDES	97
P. M. Angelopoulos, N. Kountouris, G. Anastassakis, M. Taxiarchou PARTIAL REPLACEMENT OF XANTHATE BY ORGANOSOLV LIGNIN ON PYRITE/ARSENOPYRITE FLOTATION	103
K. Hružová, July Ann Bazar, Leonidas Matsakas, Anders Sand, Ulrika Rova, Paul Christakopoulos ORGANOSOLV LIGNIN PARTICLES: A NOVEL GREEN REAGENT THAT INCREASES THE FLOTATION EFFICIENCY OF SULFIDE ORES	109
A. Peppas, D. Skenderas, P.M. Angelopoulos, C. Politi ENVIRONMENTAL BENEFITS OF LIGNIN BASED ECOFRIENDLY SURFACTANTS FOR FLOTATION PROCESSES TOWARDS CURRENT PRACTICES	115

A. Peppas, K. Hurzova, D. Skenderas, C. Politi, L. Matsakas, P.M. Angelopoulos EVALUATION OF BATTERY MINERALS FLOTATION PROCESS ECO FRIENDLINESS UTILISING BIODEGRADABLE LIGNIN REAGENTS	121
A. Peppas, C. Politi, D. Skenderas, P.M. Angelopoulos ENVIRONMENTAL ASSESSMENT OF RARE EARTHS RECOVERY METHOD FROM BAUXITE RESIDUES	126
PAPERS	133
A. Jankovic, M. Sederkennya MODIFIED BOND AND RITTINGER ENERGY-SIZE RELATIONSHIPS FOR LABORATORY FINE GRINDING	135
V. Nikolić, M. Trumić, D. Tanikić OPTIMIZATION OF MICRONIZING ZEOLITE GRINDING USING ARTIFICIAL NEURAL NETWORKS	143
E. Petrakis, K. Komnitsas THE EFFECT OF MICROWAVE RADIATION ON DRY GRINDING KINETICS OF BAUXITE ORE	150
M.H. Tyeb, S. Mishra, A.K. Majumder LSTM AND CNN COMBINATION BASED MODELLING APPROACH FOR PARTITION CURVE PREDICTION IN HYDROCYCLONES	157
I. Jovanović, M.Ž. Trumić, J. Sokolović, M.S. Trumić, J. Nešković DETERMINATION OF LIMITING SETTLING VELOCITY IN THE SLURRY PIPELINE FROM GRINDING PLANT, USING DIFFERENT APPROACHES – A CASE STUDY	163
N. Omarova, R. Sherembayeva, A.Amirkhan, Zh. Ibraybekov, A. Nesipbay FLOTATION OF POLYMETALLIC LEAD-ZINC ORES OF THE BAKALSKOYE DEPOSIT	168
V.A. Chanturiya, I.Zh. Bunin, M.V. Ryazantseva THE APPLICATION OF THE DIELECTRIC BARRIER DISCHARGE (DBD) FOR THE IMPROVEMENT OF THE SEPARATION OF PYRITE AND ARSENOPYRITE	174
V. Ignatkina, A. Kayumov, N. Yergesheva, P. Chernova BASIC SELECTIVE REAGENT REGIMES FOR COMPLEX SULFIDE ORE FLOTATION	179
S. Chaudhuri, S. Maity, S.C. Maji, D. Roy, U.S. Chattopadhyay STUDIES ON THE FLOATABILITY CHARACTERISTICS OF LOW VOLATILE COKING COAL FINES USING X-RAY DIFFRACTION (XRD) ANALYSIS AS A DIAGNOSTIC TOOL	186
V.I. Ryaboi, V.P. Kretov, E.D. Schepeta, I.V. Ryaboi, S.E. Levkovets APPLICATION OF COLLECTOR BTF-15221 IN FLOTATION OF COPPER- AND GOLD - CONTAINING ORES	193
I. Dervišević, A. Dervišević, M. Tomović, J. Galjak COMPARATIVE ANALYSIS OF REAGENTS FOR GOLD EXTRACTION FROM FLOTATION TAILS	202
E.M.S. Silva, A.C. Silva, J.M.B.S. Cabral, P.S. Oliveira, A.F. Nascimento, A.P. Vieira Filho, S.A. Santos TESTS WITH DIFFERENT FLOCCULANTS FOR CHROMIUM ORE TAILINGS	208
C. Ouyang, B. Lv, K. Jia, Y. Yang STUDY ON THE APPLICATION OF HIGH-EFFICIENCY AND ENVIRONMENT-FRIENDLY COPPER COLLECTOR TO ASSOCIATED COPPER IN AN IRON ORE	214
S. Sredić, Lj.Tankosić KINETIC STUDIES OF THE ADSORPTION POLYACRILAMIDE-BASED FLOCCULANTS ON NATURAL GOETHITE, QUARTZ AND CLAY MINERALS	221

G. D. Bogdanović, D. Marilović, B. Nikolić, S. J. Petrović COLUMN LEACHING OF LOW-GRADE COPPER SULFIDE ORE WITH SULFURIC ACID	230
K. Gáborová, M. Achimovičová, M. Hegedüs, O. Šestinová AN INFLUENCE OF MECHANICAL ACTIVATION ON THE COPPER LEACHING KINETICS OF BERZELIANITE	236
D. Medić, I. Đorđević, M. Nujkić, A. Papludis, V. Nedelkovski, S. Alagić, S. Milić USE OF COPPER POWDER AS A REDUCING AGENT IN THE LEACHING PROCESS OF LiCoO_2	242
J. Dimitrijević, S. Jevtić, A. Marinković, M. Simić, M. Koprivica, J. Petrović REMOVAL OF HEAVY METAL IONS FROM MULTIMETALLIC SOLUTION BY MODIFIED OAT STRAW	248
M.R. Rath, A.S. Patra, S. Kiran Kumar, M. Mukherjee, A. Chatterjee, A. Ranjan, A.K. Bhatnagar, A.K. Mukherjee A PROCESS TO DECREASE THE CLAY COATING OF IRON ORE LUMPS & FINES BY THE APPLICATION OF DISPERSANTS	254
H. Kurama, S. Kurama SURFACTANTS AND THEIR FUNCTIONS ON NANO-POWDER SYNTHESIS	262
A. Goryachev, D. Makarov METHODS FOR PROCESSING NATURAL AND ANTHROPOGENIC COPPER- NICKEL RAW MATERIALS IN THE ARCTIC	275
Y. Yuankun, D. Mirović DAM BREACH ANALYSIS USING HEC-RAS: A CASE STUDY OF COPPER AND GOLD "ČUKARU PEKI" MINE DAMS	283
A. Milovanović Brkić, Y. Yuankun, N. Buđelan MANAGEMENT OF FLOTATION TAILINGS AS MINING WASTE ON THE COPPER AND GOLD MINE "CUKARU PEKI"	289
N. Pavlovic, F. Palkovits, A. Hall GEO-STABLE DISPOSAL OF COAL COMBUSTION BYPRODUCTS	297
N. Pavlovic, F. Palkovits, A. Hall TAIL WAGGING THE DOG-WHY INTEGRATED SOLUTIONS ARE BETTER-TAILINGS AND BACKFILL DISPOSAL	303
V. Alivojvodic, N. Petrovnijevic POSITION OF COPPER WITHIN URBAN MINING - RECOVERING POTENTIAL FROM MINE TAILINGS	309
V.Tsitsishvili, N.Dolaberidze, N.Mirdzveli, M.Nijaradze, Z.Amiridze, B.Khutsishvili BACTERIOSTATIC ACTIVITY OF GEORGIAN HEULANDITE ENRICHED WITH BIOLOGICALLY ACTIVE METALS	315
V.Tsitsishvili, M.Panayotova, N.Dolaberidze, N.Mirdzveli, M.Nijaradze, Z.Amiridze, B.Khutsishvili, N.Jakipbekova, S.Sakibayeva THERMAL STABILITY OF NATURAL HEULANDITE-CHABAZITE MIXTURES	321
V.Tsitsishvili, M.Panayotova, N.Dolaberidze, N.Mirdzveli, M.Nijaradze, Z.Amiridze, B.Khutsishvili, N.Klarjeishvili, N.Jakipbekova COMPOSITION OF GEORGIAN AND KAZAKHSTANI NATURAL HEULANDITES	327
S. Matijašević, S. Grujić, V. Topalović, J. Stojanović, J. Nikolić, V. Savić, S. Zildžović NANOCRYSTALLIZATION OF POTASSIUM NIOBIUM GERMANATE GLASSES	333

A.C. Silva, E.M.S. Silva, P.S. Oliveira, A.F. Nascimento, A.P. Vieira Filho, D.B. Carvalho Neto ESTIMATING THE ACCURACY, PRECISION, AND RECALL OF THE HAND-SORTING OF A BRAZILIAN CHROMIUM ORE	338
V.V. Morozov, Y.P. Morozov, G. Zorigt, D. Lodoy, E. Jargalsaikhan, I.V. Pestriak SCANNING FLATBED OPTICAL ORE QUALITY ANALYZER	344
B. B. Tchouffa, N. J. Ndemou, M. G. Frida Ntsama CHARACTERIZATION, ENRICHMENT TEST AND VALORIZATION OF IRON ORE FROM NABEBA (NORTH – CONGO)	350
K. Jia, S. Đorđević, C. Ouyang, B. Lv LABORATORY BENEFICIATION TECHNOLOGY AND DEVELOPMENT RESEARCH ON TITANIUM MAGNETITE ORE	355
D. S. Radulović, V. Jovanović, B. Ivošević, D. Todorović, S. Milićević, M. Marković INVESTIGATION OF THE POSSIBILITY OF VALORIZATION OF TWO BORATE SAMPLES FROM THE DEPOSIT "POBRĐE" – BALJEVAC	361
S. Hredzák, M. Matik, O. Šestinová, A. Zubrik, D. Kupka, S. Dolinská, I. Znamenáčková, M. Sisol, M. Marcin, L. Pašek STUDY OF ORE SAMPLES FROM THE ZLATÉ HORY DEPOSIT (HRUBÝ JESENÍK Mts., SILESIA, CZECH REPUBLIC)	367
J. Sokolović, I. Ilić, D. Krstić COMPARISON OF THE RESULTS OF SEPARATION OF DIFFERENT COALS IN THE ANTHRACITE MINE "VRSKA CUKA"	373
B.R. Reddy, K. Abhishek, J.M. Korath, M.R Rath A COMPUTATIONAL TOOL FOR PREDICTION OF JIG CONCENTRATOR OPERATING PARAMETER TO GET IMPROVED YIELD OF CONCENTRATE	379
I. Jovanović, V. Conić, D. Milanović, F. Nakhaei, S. Krstić RELATIVE PREDICTION ERROR OF FLOTATION INDICES BY ANFIS MODELS	387
Z. Štirbanović, R. Stanojlović, J. Sokolović, D. Stanujkić, N. Čirić, I. Miljanović, G. Popović APPLICATION OF VIKOR METHOD FOR SELECTION OF COLLECTOR IN PORPHYRY COPPER ORE FLOTATION	391
S. Milutinović, Lj. Obradović, S. Petrović S. Magdalinović, I. Svrkota RANKING OF FLOTATION TAILINGS POND IN EASTERN SERBIA USING THE AHP METHOD	398
I. Jovanović, V. Conić, J. Sokolović, D. Kržanović, D. Radulović SIMPLE FUZZY MODELS FOR PREDICTION OF FLOTATION INDICES	404
S. Mishra, M.H. Tyeb, A.K. Majumder DEVELOPMENT OF A VIBRATION SENSOR-BASED ONLINE MONITORING SYSTEM FOR DETECTING ROPING IN HYDROCYCLONES	410
B. Farkaš, A. Hrastov, E. Orbanic THE IMPROVEMENT OF MINERAL PROCESSING – CASE STUDY	416
T. Mohit, P. Patel, P. Kaushal, J. Sahoo, V. Arumuru, B. Deo, M. Jain, R. Manchanda IMPROVED ON-LINE FAILURE PREDICTION METHOD OF COAL INJECTION SYSTEM USED IN A SPONGE IRON ROTARY KILN	423
M. Mikić, R. Rajković, S. Trujić, D. Kržanović, M. Jovanović IMPACT ON THE ENVIRONMENT AND OF THE OPEN MINE AND LANDFILLS IN SOUTH MINING DISTRICT – MAJDANPEK	429

M. Jovanović, D. Kržanović, R. Rajković, M. Mikić, M. Maksimović APPLICATION OF GEOGRIDS IN RECULTIVATION MEASURES AGAINST LAND DEGRADATION	435
V. Gardić, R. Marković, Z. Stevanović, A. Isvoran, T. Marković APPLICATION OF SUSTAINABLE CYCLING MANAGEMENT SYSTEM IN PHYTOREMEDIATION TECHNOLOGY OF CONTAMINATED SOILS	441
D. Đurđević-Milošević, A. Petrović, J. Elez, G. Gagula, V. Kalaba SUSTAINABLE APPROACH TO THE LACTIC ACID PRODUCTION AND ANTIBACTERIAL USE	445
B. Cekova, M. Matlievska, M. M. Puncheva, V. Velkoski, B. Kuzmanovski DIGITALIZATION OF WASTE, WAYS FOR MORE EFFICIENT WASTE MANAGEMENT	451
A. Vasileiadou, S. Zoras, A. Dimoudi INVESTIGATION OF SLAGGING CHARACTERISTICS OF INDUSTRIAL SOLID WASTES	458
A. Vasileiadou, S. Zoras, A. Dimoudi MODELLING OF CO _x AND NO _x EMISSIONS FROM INDUSTRIAL SOLID WASTES COMBUSTION USING ANSYS CHEMKIN PRO	464
Z. Bayer Ozturk, S. Kurama, A. Eser THE USAGE AND EFFECT OF BASALT CUTTING WASTE (BCW) IN CERAMIC GLAZE COMPOSITIONS CONTAINING OPAQUE AND MATT FRIT	470
D. Dinić, S. Stupar, N. Jovanović, M. Tanić, S. Jevtić SYNTHESIS AND CHARACTERIZATION OF POROUS CERAMICS BASED ON COPPER SLAG	480
M. Šišić, Dž. Dautbegović, M. Duraković ANALYSIS OF THE CHARACTERISTICS OF SLAG FROM METALLURGICAL PLANTS IN ZENICA DISPOSED OF INDUSTRIAL WASTE LANDFILL "RACA"	486
Dz. Datubegovic, M. Hasanbasic, M. Sisic, V. Birdahic ANALYSIS OF THE IMPACT OF THE INTRODUCTION OF LARGER CONTAINERS INTO THE WASTE COLLECTION SYSTEM IN THE CITY OF ZENICA	492
N. Bušatlić, I. Bušatlić, A. Halilović, N. Merdić, L. Kovač ENVIRONMENTALLY ACCEPTABLE CEMENTS WITH THE ADDITION OF GRANULATED BLAST FURNACE SLAG	498
A. Stojićević, M. Antić, M. Purić VEGETABLE INDUSTRY BY-PRODUCTS AS RAW MATERIALS IN FUNCTIONAL FOOD PRODUCTION	507
A. Petrović, R. Marković, D. Božić CARBON NANOTUBES AS POTENTIAL MATERIAL FOR WASTEWATER TREATMENT - A REVIEW	514
M. Marić, A. Ivković, B. Ivković, A. Janošević Ležaić, S. Uskoković-Marković, J. Savić, M. Milojević-Rakić, D. Bajuk-Bogdanović REMOVAL OF METHYLENE BLUE FROM AQUEOUS SOLUTIONS USING AN IRON-RICH SOIL	519
R. Marković, V. Gardić, R. Kovačević, Zoran Stevanović, A. Isvoran, V. Marjanović, A. Petrović BOR DISCRIT RIVERS WATERCOURSES CONTAMINATION BY Cu AND Ni IONS	524
P. Kekarjawlekar, N. Kamal, K. Maniyar, B. Deo, P. Nanda, P. Malakar, R. Manchanda DEVELOPING SAFE OPERATING PRACTICES (SOP) FOR POSTCOMBUSTION CHAMBER IN A SPONGE IRON PLANT	530

D. Milošević, M. Radosavljević, S. Polavder, Ž. Praštalo ARRANGEMENT OF FIELDS DEVASTATED BY CONSTRUCTION OF MAIN GAS PIPELINE	536
D. Đurđević-Milošević, A. Petrović, J. Elez, V. Kalaba, G. Gagula ENVIRONMENTAL PROTECTION THROUGH THE RATIONAL USE OF SODIUM HYPOCHLORITE AS A FUNGICIDE	542
G. Kyparissis, A. Goulkoudis, G. Papadimas, E. Tasiopoulos, A. Vasileiadou CASE STUDY OF ENERGY SAVING IN A PUBLIC SCHOOL THROUGH THE INSTALLATION OF A PHOTOVOLTAIC SYSTEM ON THE ROOF	548
D. Topalović, J. Marković, M. Jović, S. Dragović, I. Smičiklas THE ARSENIC SORPTION CAPACITY OF DIFFERENT SERBIAN SOILS	554
F. Popescu, M. Zot, E.A. Laza USING SHERPA TOOL FOR ASSESSMENT OF EUROPEAN WATERBORNE TRANSPORT SECTOR IMPACT ON AIR QUALITY	560
A. Stojić, D. Tanikić, E. Požega THE IMPACT OF EXPLOITATION OF PRIMARY AND ALTERNATIVE ENERGY SOURCES ON THE ENVIRONMENT	566
A. Radojević, S. Šerbula, T. Kalinović, J. Milosavljević, J. Kalinović MOBILE PHONES – A VALUABLE COMPONENT OF E-WASTE STREAM	572
K. Janković, M. Stojanović, D. Bojović, A. Terzić, S. Stanković APPLICATION OF COAL COMBUSTION BYPRODUCTS IN SELF-COMPACTING CONCRETE: INFLUENCE ON FLOWABILITY	579
D. Radosavljević, A. Jelić, M. Stamenović IMPACT OF STUDENT MIGRATIONS ON SUSTAINABLE AND TECHNOLOGICAL DEVELOPMENTS OF THE REPUBLIC OF SERBIA	585
D. Radosavljević, A. Jelić, M. Stamenović DEVELOPMENT OF EDUCATION FOR SUSTAINABLE DEVELOPMENT AND MANAGEMENT OF RECYCLABLE WASTE IN THE REPUBLIC OF SERBIA	592
Deependra Singh SUSTAINABLE RECOVERY OF INDIAN PLACER MINERALS-THEIR DISTRIBUTION AND MINERAL ASSEMBLAGES	598
ABSTRACTS	607
M. Tasić, I. Stojković, V. Pavićević, V. Veljković SIMULATION OF HYDRODYNAMIC CAVITATION-ASSISTED BIODIESEL PRODUCTION FROM WASTE COOKING OIL USING ASPEN PLUS	609
A. Jocić, S. Marić, A. Dimitrijević RECOVERY OF METALS FROM INDUSTRIAL EFFLUENTS USING AN IONIC LIQUID-BASED STRATEGY	610
S. Marić, A. Jocić, A. Dimitrijević IONIC LIQUID-BASED TECHNOLOGY FOR METAL RECOVERY FROM ELECTRONIC WASTE	611
J. Vučićević, S. Čupić, M. Jauković, V. Đurđević, M. Stamenović, A. Božić, A. Janićijević CURRENT STATE OF THE QUALITY OF THE LUG RIVER IN THE MUNICIPALITY OF MLADENOVAC	612

D. Žnidarič THE ENERGY CRISIS AND THE EXPLOITATION OF MINERAL RESOURCES IN THE LIGHT OF INCREASING LOADS IN SPACE	613
S. Zeković A NEW GLOBAL CHALLENGES AND REGULATION FOR SUSTAINABLE SPATIAL DEVELOPMENT OF MINING	614
P.M. Angelopoulos, P. Oustadakis, G. Anastassakis, M. Georgiou, N. Kountouris HYDROTHERMAL TREATMENT OF BAUXITE RESIDUE FOR IRON RECOVERY ENHANCEMENT BY MAGNETIC SEPARATION	615
O. Ayoglu, M. Sinche-Gonzalez, M. Moilanen TEXTURAL MINERALOGICAL UNDERSTANDING OF MAGNETITE LIBERATION CONTAINING COPPER INCLUSIONS	616
M. Sinche-Gonzalez MASTER IN MINERAL PROCESING (EMJM-PROMISE) IN THE CONTEXT OF DEMAND OF CRITICAL MATERIALS AND ENERGY TRANSITION	617
ADVERTISING MATERIALS	619
Department for Mineral and Recycling Technologies	621
Serbia Zijin Mining	624
Serbia Zijin Copper	627
Analysis d.o.o.	629
tozero	631
Monicom	632
EMJM-PROMISE	633

COLUMN LEACHING OF LOW-GRADE COPPER SULFIDE ORE WITH SULFURIC ACID

G. D. Bogdanović^{1#}, D. Marilović¹, B. Nikolić², S. J. Petrović³

¹ University in Belgrade, Technical faculty in Bor, Bor, Serbia

² Jiuzhou International Construction doo Bor, Bor, Serbia

³ Mining and Metallurgy Institute Bor, Bor, Serbia

ABSTRACT – The paper presents the results of leaching of low-grade copper sulfide ore with average Cu content of 0.33% and an oxide content of about 7%. The experiments were carried out in sulfuric acid solution and with the addition of Fe(III) ions that had the role of oxidant. During the leaching period of 23 days, with sulfuric acid, the concentration of copper in the solution ranged from 0.05 to 0.230 g/dm³, and iron from 0.125 to 0.350 g/dm³. With the addition of Fe(III) ions to the process, the concentration of copper in the solution moved in the same range. These results show that a longer period is needed for the oxidation and dissolution of this raw material.


Keywords: Leaching, Copper, Sulfuric Acid, Fe(III) ions.

INTRODUCTION

Due to the low content of copper in natural deposits, today more attention is paid to the possibility of treating low-grade raw materials. Extraction of copper from such raw materials is in most cases achieved by the leaching process [1]. Percolation leaching is used for heap leaching, leaching of dump, or "in situ" leaching, i. e. it is used for leaching of raw materials that contain a low content of useful components [1,2]. For the leaching process, it is necessary to determine the chemical and mineralogical composition of the raw material.

Sulfuric acid is most often used as an agent for the leaching of copper minerals [3], and Fe(III) ions as an oxidant [4]. Copper sulfide minerals in an acidic medium is based on the following stoichiometric reactions:



Covellite:



Chalcocite:





Chalcopyrite:



[#] corresponding author: gbogdanovic@tfbor.bg.ac.rs

The dissolution of copper oxide minerals in acidic solutions is carried out mainly without the presence of oxidants, and can be represented by the following stoichiometric reactions:



Cuprite:



Tenorite:



Azurite and Malachite:



The paper presents the influence of sulfuric acid and iron (III) ions as oxidant on the leaching of low-grade copper ore.

EXPERIMENTAL

Characterization of the sample

The ore sample was dried at room temperature and crushed. Particle size distribution was determined by the sieve analysis on the standard Retsch sieve series. The granulometric composition of the sample is shown in Figure 1.

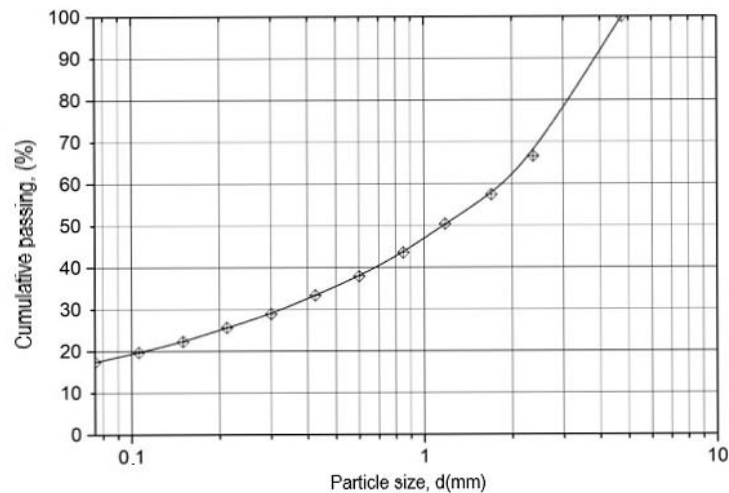


Figure 1 Particle size distribution of ore

Chemical composition of the initial sample (class -4.75 +0.00 mm) is presented in Table 1.

Table 1 Chemical composition of ore

El.	Cu _{tot}	Cu _s	S	Fe	Fe ₂ O ₃	Al ₂ O ₃	CaO	MgO	Na ₂ O	K ₂ O	SiO ₂	Zn	Ni	Mn
%	0.33	0.306	1.24	4.21	6.02	18.58	0.76	2.28	1.18	3.16	59.78	0.011	<0.007	0.052

Based on the obtained qualitative mineralogical analysis, the following mineral composition was determined: pyrite, chalcopyrite, covellite, cuprite, chalcocite, magnetite, rutile, goethite, galena, sphalerite and gangue minerals. The most present minerals were pyrite and chalcopyrite.

Column leaching

The leaching experiments were carried out in PVC columns, 110 mm in diameter and 1000 mm in height. In each column was added 7 kg of ore. At the top of the ore layer a layer of silica was placed for the uniform distribution of the acid solution. The leaching agent used in the experiment was 0.03 mol/dm³ sulfuric acid solution. When the influence of oxidants was tested, the experiments were performed with the addition of 3 g/dm³ Fe(III) ions, at a solid:liquid ratio of 1:1. The flow rate of the solution through the column during the experiment was from 8 to 10 ml/min. The ore leaching in the columns was done for 23 days. After 10 days of leaching, the flow of the leaching solution was stopped and the ore was exposed to an oxidation cycle for a period of 7 days. After the oxidation period, the sulfuric acid solution was again passed through the raw material layer in the column until the end of the leaching period.



Figure 2 Apparatus for percolation leaching

At certain time intervals, 20 cm³ of the leaching solution was sampled. Copper and iron concentrations in the solution were analyzed by Hanna HI 83200 Atomic Adsorption Spectrophotometer and Inductively Coupled Plasma Optical Emission Spectrometer (ICP-OES, Perkin Elmer Optima 8300).

RESULTS AND DISCUSSION

The results in Figure 3 show that after the initial period, which corresponds to the leaching of copper oxide, the leaching rate decreases. For the sample treated only with sulfuric acid (Fig. 3a), the concentrations of Cu and Fe in the solution increased with time in the first 11 days, and the concentration of copper was 0.158 g/dm³, and the concentration of iron was 3.037 g/dm³. The next 7 days were followed by an oxidation period. After this period, the raw material layer in the column was re-washed with a leaching solution. The concentration of Cu in the solution after the period of oxidation slight increase and reached the value of 0.182 g/dm³ and the concentration of iron in the solution remained the same (Fig. 3 a).

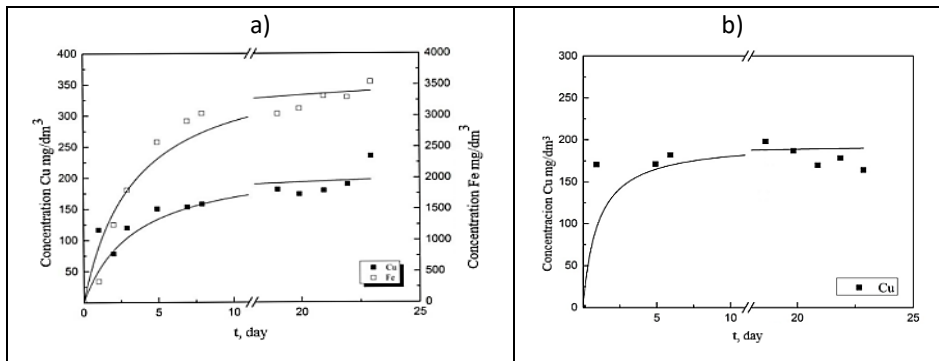


Figure 3 Concentration of Cu and Fe vs. time leaching with 0.03 mol/dm³ H₂SO₄ solution (a) and concentration of Cu vs. time leaching with 0.03 mol/dm³ H₂SO₄ and 3 g/dm³ Fe(III) ions (b)

Simultaneously with the leaching of copper oxide minerals, the process of oxidation of copper sulfide minerals takes place. Since leaching is a slow process, dissolved oxygen in the leaching solution and Fe³⁺ ions, formed by leaching of iron oxide compounds and pyrite oxidation, can also act as oxidants for copper sulfides. Under real conditions, microorganisms present in the ore can oxidize Fe²⁺ to Fe³⁺ ions, which can affect the leaching rate of copper sulfide minerals. Therefore, percolation leaching of copper on a heap or on a dump can last for years, depending on the size of the heap, i.e. the dump, the copper content in it and the used copper mineral leaching agent. Oxidation of chalcopyrite (reactions 3 and 4) leads to the formation of elemental sulfur and sulfate as the final product. Elemental sulfur formed can act as a passivating layer on the surface of a mineral that leads to slow down the dissolution rate [5-9].

During the leaching of ore in the solution of 0.03 mol/dm³ H₂SO₄ and 3 g/dm³ Fe (III) ions, the concentration of copper in solution after 11 days was 0.187 g/dm³ and after the oxidation period there was a small change in the concentration of copper in the solution (Fig. 3b).

Final copper extraction after 23 days in the sulfuric acid solution was 7.11%, and the extraction of oxide Cu was 97.87%. Under the tested conditions, the iron extraction value was 7.88%. Since during the column leaching a low extraction of total copper was obtained, and copper oxide minerals were not completely leached, it can be assumed

that there was a higher consumption of acid due to the occurrence of other reactions with carbonate minerals or iron minerals. As a result of these reactions, the formation of reaction products can prevent contact of the solution with the copper minerals [10,11].

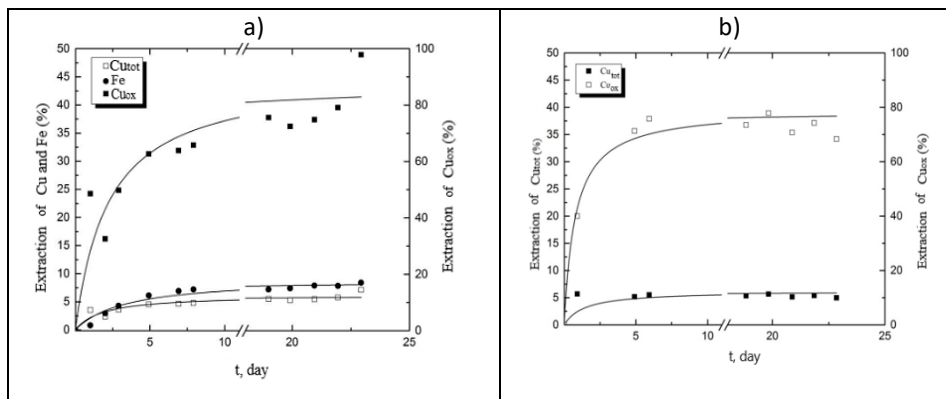


Figure 4 Extraction of Cu and Fe vs. time leaching with 0.03 mol/dm³ H₂SO₄ solution (a) and Extraction of Cu vs. time leaching in 0.03 mol/dm³ H₂SO₄ and 3 g/dm³ Fe(III) ions

The final copper extraction with the addition of Fe(III) ions was about 5.6%, while the extraction of oxide copper was about 69%. It can be seen that the addition of Fe(III) ions slightly affects the leaching of copper. Considering that copper in the sample is mostly in the form of chalcopyrite, the degree of oxidation and leaching of this raw material was very low. It can be assumed that another type of processing should be used to treat such raw material.

CONCLUSION

Percolation leaching of low-grade sulfide ore in columns performed with sulfuric acid with and without oxidants, with a period of oxidation of the sample in the columns, did not give satisfactory results. The best result was obtained by leaching with 0.03 mol/dm³ H₂SO₄ without the addition of oxidants. After 23 days of leaching in the column, the concentration of copper in the solution was 0.235 g/dm³ and the extraction of total copper was 7.11%. Considering the content of oxide minerals in the examined raw material was 7.27%, it can be concluded that the oxidation of sulfide minerals did not succeed, even part of the oxide copper remained unleached. Analyzing the obtained results, it can be concluded that another type of processing should be used for this kind of raw material.

Acknowledgment

The research presented in this paper was done with the financial support of the Ministry of Science, Technological Development and Innovation of the Republic of Serbia, within the funding of the scientific research work at the University of Belgrade, Technical Faculty in Bor, Grant No. 451-03-47/2023-01/200131 and Mining and Metallurgy Institute Bor, Grant No. 451-03-47/2023-01/200052.

REFERENCES

1. Ilankoon I.M.S.K., Tang Y., Ghorbani Y., Northey, S., Yellishetty, M., Deng, X., McBride, D. (2018) The current state and future directions of percolation leaching in the Chinese mining industry: Challenges and opportunities. *Minerals Engineering*, 125, 206-222.
2. Bogdanović, G.B., Stanković, V.D., Trumić, M.S., Antić, D.V., Trumić, M.Ž. (2016) Leaching of Low-Grade Copper Ores: A Case Study For „Kraku Bugaresku Cementacija” Deposits (Eastern Serbia). *Journal of Mining and Metallurgy*, 52 A (1) 45-56.
3. Sun, X-L., Cen, B-Z., Yang, X-Y., Liu, Y-Y. (2009) Technological conditions and kinetics of leaching copper from complex copper oxide ore. *Journal of Central South University of Technology*, 16, 936-941.
4. Li, Y., Kawashima, N., Li, J., Chandra, A.P., Gerson, A.R. (2013) A review of the structure, and fundamental mechanisms and kinetics of the leaching of chalcopyrite. *Advances in Colloid and Interface Science*, 197-198, 1-32.
5. Munoz. P.B., Miller. J. D., Wadsworth, M.E. (1979) Reaction mechanism for the acid ferric leaching of chalcopyrite. *Metallurgical Transactions B10*, 149-158.
6. Dutrizac, J.E. (1981) The dissolution of chalcopyrite in ferric sulfate and ferric chloride media. *Metallurgical Transactions*, 12B, 371-378.
7. Mateos, F. B., Perez, I. P., Mora, F. C. (1987) The passivation of chalcopyrite subjected to ferric sulfate leaching and its reactivation with metal sulfides. *Hydrometallurgy*, 19, 159-167.
8. Hackl, R.P., Dreisinger, D. B., Peters, E., King, J. A. (1995) Passivation of chalcopyrite during oxidative leaching in sulphate media. *Hydrometallurgy* 39, 25-48.
9. Bogdanović, G. D., Antonijević, M. M., Šerbula, S. M., Milić, S. M., (2007) Elektrohemijsko ponašanje halkopirita u rastvorima sumporne kiseline, *Zaštita materijala* 48 (3), 39-48.
10. de Oliveira, C.; de Lima, G.F.; de Abreu, H.A. Duarte, H.A. (2012) Reconstruction of the Chalcopyrite Surfaces: A DFT Study. *The Journal of Physical Chemistry C*, 116, 6357-6366.
11. O'Connor, G.M., Eksteen, J.J. (2020) A critical review of the passivation and semiconductor mechanisms of chalcopyrite leaching. *Miner. Eng.*, 154, 106401.



ISBN-978-86-6305-133-1

