

UNIVERSITY OF BELGRADE
TECHNICAL FACULTY BOR

**52nd International October Conference on
Mining and Metallurgy**



PROCEEDINGS

Edited by

Saša Stojadinović

and

Dejan Petrović

November 29th – 30th 2021

Bor, Serbia

UNIVERSITY OF BELGRADE
TECHNICAL FACULTY IN BOR

**52nd International October Conference on
Mining and Metallurgy**



PROCEEDINGS

Edited by

Saša Stojadinović

and

Dejan Petrović

November 29th – 30th 2021

Bor, Serbia

**52nd International October Conference
on Mining and Metallurgy, IOC 2021**

PUBLISHER:

UNIVERSITY OF BELGRADE - TECHNICAL FACULTY IN BOR, BOR, NOVEMBER 2021

FOR THE PUBLISHER:

DEAN: Prof. dr Nada Štrbac

EDITORS:

Prof. dr Saša Stojadinović

Doc. dr Dejan Petrović

TECHNICAL EDITOR

Pavle Stojković, MSc.

PRINTED BY:

»Štamparija Atlantis d.o.o.« Niš

CIRCULATION: 100 Copies

CIP – Каталогизација у публикацији –

Народна библиотека Србије, Београд

622(082)

669(082)

**INTERNATIONAL October Conference on Mining
and Metallurgy (52 ; 2021 ; Bor)**

Proceedings / 52nd International October
Conference on Mining and Metallurgy - IOC 2021,
November 29th - 30th 2021 Bor, Serbia ; [organizer]
University of Belgrade, Technical Faculty in Bor ;
[co-organizer Institute for Mining and Metallurgy
Bor] ; edited by Saša Stojadinović and Dejan
Petrović. - Bor : University of Belgrade, Technical
Faculty, 2021 (Niš : Atlantis). - V, 228 str. : ilustr. ;
25 cm

Tiraž 100. - Bibliografija uz svaki rad.

ISBN 978-86-6305-119-5

а) Рударство -- Зборници б) Металургија --
Зборници

COBISS.SR-ID 52072201

ORGANIZER:

UNIVERSITY OF BELGRADE – TECHNICAL FACULTY IN BOR

Co-ORGANIZER:

INSTITUTE FOR MINING AND METALLURGY BOR

Under the Auspice of:



**The Ministry of Education, Science and
Technological Development of the Republic of
Serbia**

CONFERENCE SPONSORS





COMMITTEES

52nd International October Conference on Mining and Metallurgy, IOC 2021

SCIENTIFIC COMMITTEE

- Prof. dr Nada Štrbac, (UB TF Bor, Serbia)
- Prof. dr Iwao Katayama, (Osaka University, Osaka, Japan)
- Prof. dr Rodoljub Stanojlović, (UB TF Bor, Serbia)
- Prof. dr Radoje Pantović, (UB TF Bor, Serbia)
- Prof. dr Jakob Lamut, (ULj FNT Ljubljana, Slovenia)
- Prof. dr Sanda Krausz, (University of Petroșani, Romania)
- Prof. dr Grozdanka Bogdanović, (UB TF Bor, Serbia)
- Prof. dr Jelena Penavin Škundrić, (TF Banja Luka, B&H)
- Prof. dr Seshadri Seetharaman, (Royal Institute of Technology, Stockholm, Sweden)
- Prof. dr Dragoslav Gusković, (UB TF Bor, Serbia)
- Prof. dr Jožef Medved, (ULj FNT Ljubljana, Slovenia)
- Dr Slavomir Hredzak, (SAS Kosice, Slovakia)
- Prof. dr Aleksandar Dimitrov, (FTM Skopje, FYR Macedonia)
- Prof. dr Karlo Raić, (UB TMF, Serbia)
- Prof. dr Snežana Šerbula, (UB TF Bor, Serbia)
- Dr Ana Kostov, (IRM Bor, Serbia)
- Prof. dr Kemal Delijić, (MTF Podgorica, Montenegro)
- Prof. dr Stoyan Groudev, (UMG "Saint Ivan Rilski" Sofia, Bulgaria)
- Dr Andrei Rotaru, (Facultatea de Mecanica, Romania)
- Prof. dr Krzysztof Fitzner, (AGH University, Krakow, Poland)
- Prof. dr Sulejman Muhamedagić, (FMM Zenica, B&H)
- Prof. dr Anđelka Mihajlov, (Educons University, Serbia)
- Prof. dr Luis Filipe Malheiros, (FEUP, Porto, Portugal)
- Prof. dr Svetlana Ivanov, (UB TF Bor, Serbia)
- Prof. dr Batrić Pešić, (Materials Science Faculty, Idaho, USA)
- Prof. dr Ljubica Ivanić, (UB TF Bor, Serbia)
- Dr Srećko Stopić, (RWTH Aachen, IME Aachen, Germany)
- Prof. dr Boštjan Markoli, (ULj FNT Ljubljana, Slovenia)
- Dr Magnus Ericsson, (Lulea Technical University, Stockholm, Sweden)
- Prof. dr Tamara Holjevac Grgurić, (MF Sisak, Croatia)
- Prof. dr Boyan Boyanov, (University Paisiy Hilendarski, Plovdiv, Bulgaria)
- Prof. dr Milan Antonijević, (UB TF Bor, Serbia)
- Prof. dr Tatjana Volkov-Husović, (UB TMF, Serbia)
- Prof. dr Branka Jordović, (TF Čačak, Serbia)
- Prof. dr Milan Trumić, (UB TF Bor, Serbia)
- Prof. dr Tomaš Havlik, (TUKE, Slovakia)
- Prof. dr Carl Heinz Spitzer, (TU Clausthal, Germany)
- Dr Mile Bugarin, (IRM Bor, Serbia)
- Prof. dr Velizar Stanković, (UB TF Bor, Serbia)
- Prof. dr Costas Matis, (AU Thessaloniki, Greece)
- Dr Milenko Ljubojev, (IRM Bor, Serbia)
- Prof. dr Velimir Radmilović, (University of California at Berkeley, USA)
- Prof. dr Dejan Tanikić, (UB TF Bor, Serbia)
- Dr Mirjam Jan-Blažič, (Slovenian Foundryen Society, Slovenia)
- Prof. dr Vitomir Milić, (UB TF Bor, Serbia)

Prof. dr Desimir Marković, (UB TF Bor, Serbia)

Prof. dr Mirjana Rajčić Vujašinović, (UB TF Bor, Serbia)

Dr Vladan Ćosović, (UB IHTM, Serbia)

Prof. dr Dimitris Panias, (NTUA, Athens, Greece)

Prof. dr Mirko Gojić, (MF Sisak, Croatia)

Prof. dr Vladimir Krstić, (Queen's University, Canada)

Prof. dr Dimitriu Sorin, (Polytechnic University of Bucharest, Romania)

Dr Miroslav Sokić, (UB ITNMS, Serbia)

Prof. dr Vladislav Kecojević, (West Virginia University, USA)

Prof. dr Dragan Manasijević, (UB TF Bor, Serbia)

Prof. dr Mirsada Oruč, (FMM Zenica, B&H)

Prof. dr Vlastimir Trujić, (IRM Bor, Serbia)

ORGANIZING COMMITTEE

Prof. dr Saša Stojadinović, vanredni profesor, UB, TF Bor

Prof. dr Ljubiša Balanović, vanredni profesor, UB, TF Bor

Doc. dr Dejan Petrović, docent, UB, TF Bor

dr Ana Kostov, naučni savetnik, Institut za rudarstvo i metalurgiju Bor

Doc. dr Aleksandra Mitovski, docent, UB, TF Bor

Doc. dr Ana Simonović, docent, UB, TF Bor

Prof. dr Jovica Sokolović, vanredni profesor, UB, TF Bor

Prof. dr Đorđe Nikolić, redovni profesor, UB, TF Bor

Doc. dr Uroš Stamenković, docent, UB, TF Bor

Prof. dr Milan Radovanović, vanredni profesor, UB, TF Bor

Doc. dr Danijela Voza, docent, UB, TF Bor

Jelena Ivaz, asistent, UB, TF Bor

Pavle Stojković, asistent, UB, TF Bor

Mladen Radovanović, asistent, UB, TF Bor

Predrag Stolić, asistent, UB, TF Bor

Kristina Božinović, asistent, UB, TF Bor

Sandra Vasković, Nastavnik engleskog jezika, UB, TF Bor

Oliver Marković, šef IKTC, UB, TF Bor

Miomir Voza, laborant, UB, TF Bor

TABLE OF CONTENTS

Aleksandra Milosavljević	
THE COMPLEXITY OF SEM-EDS – WHAT AFFECTS THE QUALITY OF OBTAINED RESULTS?	1
Zoran Karastojković, R Perić, M Srečković	
LASER QUENCHING OF CUTTING TOOL STEELS - A REVIEW	5
Slavica Miletić, D Bogdanović, E Požega	
IMPACT OF EXTRAORDINARY SECURITY MEASURES TO EMPLOYEES DURING THE PANDEMIC COVID-9	15
Daniela Grigorova, R Paunova	
KINETIC STUDY OF SOLID-PHASE REDUCTION OF POLYGRADIENT IRON-CONTAINING MATERIAL	19
Emina Požega, D Simonović, S Marjanović, M Jovanović, L Gomidželović, M Mitrović, Z Stanojević Šimšić	
PART I: WHAT MAKES A GOOD THERMOELECTRIC	23
Emina Požega, D Simonović, S Marjanović, M Jovanović, L Gomidželović, M Mitrović, S Miletić	
PART II: WHAT MAKES A GOOD THERMOELECTRIC	27
Dragan Manasijević, Lj Balanović, I Marković, M Gorgievski, U Stamenković, K Božinović, D Minić, M Premović	
STUDY OF MICROSTRUCTURE AND THERMAL CONDUCTIVITY OF THE Ag–Bi–Sn ALLOYS	31
Vladimir S. Topalović, S Matijašević, S Grujić, J Stojanović, J Nikolić, V Savić, S Zildžović	
THE INFLUENCE OF THE PARTICLE SIZE ON CRYSTALLIZATION OF GLASS POWDERS FROM THE SYSTEM $\text{Li}_2\text{O}-\text{Al}_2\text{O}_3-\text{GeO}_2-\text{P}_2\text{O}_5$	35
Vesna Marjanović, R Marković, V Krstić	
TECHNOLOGIES FOR PHYSICAL TREATMENT OF WATER CONTAINING SELENIUM: A REVIEW	39
Vesna Marjanović, R Marković, V Krstić	
TECHNOLOGIES FOR BIOLOGICAL TREATMENT OF WATER CONTAINING SELENIUM: A REVIEW	43
Milenko Jovanović, M Mikić, M Maksimović, D Kržanović, R Rajković, E Požega	
USAGE SPECIFICS OF GEOGRIDS	47

Srećko Manasijević, Z Zovko Brodarac, N Dolić, M Djurdjević, R Radiša	
INTERMETALLIC BONDING BETWEEN A RING CARRIER AND AN ALUMINUM PISTON ALLOY	51
Snežana Šarboh	
PATENTED INVENTIONS OF LJUBOMIR KLERIĆ	55
Miomir Mikic, M Jovanović, R Rajković, D Kržanović, E Požega	
DEGRADED AREA OF VELIKI KRIVELJ QUARRY RECULTIVATION	59
Dragana Adamović, D Ishiyama, H Kawaraya, O Yasumasa	
EFFECTS OF TAILINGS ON GROUNDWATER ALONG BOR AND BELA RIVERS IN THE BOR MINING AREA, EASTERN SERBIA	63
Ana Kostov, Z Stanojević Šimšić, A Milosavljević,	
CHARACTERIZATION OF ALLOYS CuAlAu0.5	67
Marija Milenković, V Jovanović, J Paunković, V Krstić	
MULTICRITERIA ANALYSIS OF THE LEVEL OF SUSTAINABLE DEVELOPMENT OF THE TOPLICA DISTRICT USING THE ELECTRE METHOD	71
Daniel Kržanović, R Rajković, D Stevanović, M Mikić, M Jovanović, S Petrović	
LONG-TERM PLANNING OF MINING THE LEAD AND ZINC ORE DEPOSIT IN THE BRSKOVO ORE FIELD, THE REPUBLIC OF MONTENEGRO	75
Radmilo Rajković, D Kržanović, M Mikić, M Jovanović	
CALCULATION OF SAFETY DISTANCE FOR THE OPERATION OF MINING EQUIPMENT IN THE WORKING ENVIRONMENT WITH WEAKENED CHARACTERISTICS AT THE OPEN PIT "NORTH MINING DISTRICT" OF THE COPPER MINE MAJDANPEK	79
Zdenka Stanojević Šimšić, A Kostov, A Milosavljević, E Požega	
HARDNESS, MICROHARDNESS AND ELECTROCONDUCTIVITY OF ALLOYS WITH VARIABLE Cu CONTENT IN Cu-Al-Ag SYSTEM	83
Miodrag Banješević	
STRATIGRAPHY AND AGE OF ROCK UNITS AND MINERALIZATION IN THE TIMOK MAGMATIC COMPLEX AND THE BOR METALLOGENIC ZONE – A REVIEW	87
Milan Radivojević, Z Stević, M Tanasković	
DUALPHASED FOURWAY INTERSECTION REGULATED BY TRAFFIC LIGHTS WITH FIXED AND ADAPTIVE MOD OF OPERATION	93
Filip Gramić, N Rančić, S Filipović, J Đorđević	
USE OF COPPER TAILING AND COPPER SLAG IN 3D PRINTED CONCRETE PROCESSES	97
Filip Gramić, N Rančić, S Filipović, J Đorđević,	
POSSIBILITY OF USING MINING WASTE IN THE PRODUCTION OF BRICK PRODUCTS	101

Stepan O. Vidysh

GOLD-SILVER ALLOYS ANODIC DISSOLUTION RESEARCH IN HYDROCHLORIC ACID ELECTROLYTES 105

Milan Gorgievski, M Marković, D Božić, Vr Stanković, N Štrbac, V Grekulović, M Zdravković

ADSORPTION ISOTHERMS FOR COPPER IONS ADSORPTION ONTO WALNUT SHELLS 109

Miljan Marković, M Gorgievski, N Štrbac, V Grekulović, A Mitovski, K Božinović, M Zdravković

pH AND CONDUCTIVITY CHANGE DURING THE RINSING AND ADSORPTION OF COPPER IONS ONTO WALNUT SHELLS 113

Vesna Grekulović, A Mitovski, M Rajčić Vujasinović, N Štrbac, M Zdravković, M Gorgievski, M Marković

ELECTROCHEMICAL BEHAVIOR OF COPPER IN CHLORIDE MEDIUM IN THE PRESENCE OF WALNUT SHELL MACERATE 117

Marija Šljivić-Ivanović, S Dimović, I Jelić,

EXPERIMENTAL DESIGN APPROACH IN RADIONUCLIDE SORPTION 121

Ivana Jelić, A Savić, M Šljivić-Ivanović, S Dimović

INFLUENCE OF SILICA FUME ON SCC CONCRETE PROPERTIES 125

Milan Radovanović, A Simonović, M Petrović Mihajlović, Ž Tasić, V Nedelkovski, M Antonijević

L-LYSINE AS CORROSION INHIBITOR OF STAINLESS STEEL IN RINGER'S SOLUTION 129

Dragana Marilović, M Trumić, M Trumić, Lj Andrić

THE INFLUENCE OF CALCIUM IONS ON DEINKING FLOTATION RECOVERY UNDER DIFFERENT CONDITIONS 133

Dragana Medić, S Milić, S Alagić, M Nujkić, S Đorđević, A Papludis

OPTIMIZATION OF CATHODIC MATERIAL LEACHING PROCESS IN ACID-SULPHATE SOLUTION 137

Milijana Mitrović, D Gusković, S Marjanović, B Trumić, E Požega, U Stamenković, J Petrović

OBTAINING MULTILAYER COPPER STRIPS BY ARB (ACCUMULATIVE ROLL BONDING) ROLLING PROCESS 141

Nataša Đorđević, S Mihajlović, N Obradović, A Peleš, S Filipović

THE INFLUENCE OF HIGH COMPACTION PRESSURE ON CORDIERITE-BASED CERAMICS 145

Nataša Đorđević, S Mihajlović, M Sokić, B Marković

SEM AND X-RAY ANALYSES OF SINTERED MgO / Bi₂O₃ BINARY SYSTEM 149

Ivana Ilić, J Sokolović, M Trumić, Z Stirbanović	
COMPARATIVE RESULTS OF COPPER FLOTATION FROM SLAG BEFORE AND AFTER THE PROCESS OF MAGNETIC CONCENTRATION	153
Daniela Grigorova	
FERROSILICON OBTAINING USING IRON-SILICATE –FAYALITE	157
Slavica Mihajlović, M Jovanović, N Đorđević, A Patarić, M Vlahović, V Kašić	
THE CLAY PRELIMINARY TESTING FROM MUNICIPALITY AREA OF REKOVAC	161
Milan Milosavljević, M Premović, D Minić, Dn Mansijević, Ar Đorđević, M Kolarević	
EXPERIMENTAL AND THERMODYNAMIC STUDY OF ISOTHERMAL SECTIONS AT 600 °C AND 400 °C OF TERNARY Bi-Cu-Ge SYSTEM	165
Aleksandar Đorđević, D Minić, M Premović, D Mansijević, M Milosavljević, V Ristić	
STUDY OF TEMPERATURE PHASE TRANSFORMATION OF THE TERNARY Bi-Cu-Ge SYSTEM	169
Aleksandar Savić, I Jelić, M Šljivić-Ivanović, S Dimović, N Pudar, A Pfandler	
RECYCLED COARSE AGGREGATE AND FLY ASH EFFECT ON COMPRESSIVE STRENGTH OF SELF-COMPACTING CONCRETE	173
Vladan Kašić, D Životić, V Simić, A Radosavljević-Mihajlović, J Stojanović, S Mihajlović, M Vukadinović	
FORECAST RESOURCES OF ZEOLITHIC TUFFS OF SERBIA	177
Vladan Kašić, A Radosavljević-Mihajlović, S Radosavljević, J Stojanović, S Mihajlović, M Vukadinović	
GEOLOGICAL AND MINERAL CHARACTERISTICS OF ZEOLITHIC TUFF TOPONICA DEPOSITS NEAR KOSOVSKA KAMENICA	181
Konstantin Petkov, V Stefanova, P Iliev	
METHOD FOR UTILIZATION OF THE SULFURIC ACID OBTAINED DURING AUTOCLAVE DISSOLUTION OF PYRITE CONCENTRATE	185
Stefan Đorđević, D Ishiyama, Y Ogawa, Z Stevanović, O Osenyeng, D Adamović, V Trifunović	
MONITORING OF pH VALUE AND CONCENTRATION OF COPPER IN RIVERS DOWNSTREAM FROM BOR MINE IN PERIOD 2015-2021	189
Viša Tasić, M Cocić, B Radović, T Apostolovski-Trujić	
CHEMICAL COMPOSITION OF PARTICULATE MATTER IN THE INDOOR AIR AT THE TECHNICAL FACULTY IN BOR (SERBIA)	193
Snežana Ignjatović, I Vasiljević, M Negovanović	
DEFINING STRUCTURAL CORRELATION USING OF TOTAL HORIZONTAL GRADIENT	197

Velizar Stanković, M Janošević

**INCREASING THE CAPACITY OF THE COPPER SMELTING COMPANY IN THE COMPANY
"SERBIA ZIJIN COPPER" - CHALLENGES AND CONSEQUENCES TO THE ENVIRONMENT** 201

Vladimir Jovanović, D Todorović, B Ivošević, D Radulović, S Milićević, D Nišić

**CHARACTERIZATION OF PELLET SAMPLES OBTAINED BY PELETIZATION OF LIMESTONE
AND SEAWEED** 205

Vanja Trifunović, L Avramović, R Jonović, S Milić, S Đorđievski, M Jonović

**HYDROMETALLURGICAL TREATMENT OF ELECTIRIC ARC FURNACE DUST IN AIM OF ZINC
SEPARATION** 209

Jovana Bošnjaković, N Knežević, N Čutović, M Bugarčić, A Jovanović, Z Veličković, S
Manasijević

**EVALUATION OF ADSORPTION PERFORMANCE OF PHOSPHATES REMOVAL USING CELL-
MG HYBRID ADSORBENT** 213

Dragan Radulović, Lj Andrić, D Božović, V Jovanović, B Ivošević, D Todorović,

**POSSIBILITY OF USING LIMESTONE FROM "PJEŠIVAČKI DO"-DANILOVGRAD DEPOSIT AS
FILLER IN VARIOUS INDUSTRY BRANCHES** 217

Predrag Stolić, J Ivaz, D Petrović, Zoran Stević

**ADVANTAGES OF MINING ENGINEERING CURRICULUM REALIZATION USING
SOLUTIONS BASED ON FREE SOFTWARE** 221

Slađana Krstić, E Požega, S Petrović, S Magdalinović, D Urošević, S Miletić, Z Stojanović
Šimšić

**QUALITY INVESTIGATION OF SAND FOR THE PRODUCTION OF AGGREGATES ON
VINOGRADI LOCALITY (DELIBLATSKA PEŠČARA)** 225

Saša Marjanović, D Gusković, M Mitrović, E Požega ,B Trumić, U Stamenković

**INFLUENCE OF COLD ROLLING AND ANNEALING ON HARDNESS OF BIMETALLIC STRIP
Cu– Al** 229

HYDROMETALLURGICAL TREATMENT OF ELECTRIC ARC FURNACE DUST IN AIM OF ZINC SEPARATION

Vanja Trifunović¹, Ljiljana Avramović¹, Radojka Jonović¹, Snežana Milić², Stefan Đorđević¹, Marko Jonović³

¹Mining and Metallurgy Institute Bor, Zelenibulevar 35, 19210 Bor, Serbia

²University in Belgrade, Technical Faculty in Bor, Vojske Jugoslavije 12, 19210 Bor, Serbia

³Institute of Chemistry, Technology and Metallurgy, Njegoševa 12, 11000 Belgrade, Serbia

Abstract

During the steel production from secondary raw materials in the electric arc furnace, generation of the main intermediate of the process- dust from the electric arc furnace (EAF dust) occurs. This dust contains significant amounts of Zn and Fe, as well as Pb, Ca, Mn, Ni, Cu, Cd, Mg, Si, Cr, F, Cl and other elements and is considered hazardous industrial solid waste since it contains heavy metals. In order to separate Zn as a valuable component, hydrometallurgical treatment of EAF dust was investigated. The treatment consists of two stages: 1st stage is water leaching of EAF dust performed in order to remove water-soluble compounds, and 2nd stage is acid leaching in order to leach ZnO from EAF dust and obtain a ZnSO₄ solution. With optimal parameters of the water leaching process of EAF dust, the achieved leaching rates of water-soluble compounds are as follows: 80.84% Cl, 60.63% K, 52.95% Na, 18.23% Ca, while with acid leaching of the solid residue obtained after water leaching at optimal parameters achieved leaching rate of Zn is 82.34%. In addition to the economic aspect of this treatment where the separation of Zn from EAF dust is performed, the treatment also has an ecological aspect because the transformation of hazardous waste into non-hazardous waste is performed, which has a positive effect on the environment.

Keywords: EAF dust, hydrometallurgical treatment, Zn separation, environment protection.

1. INTRODUCTION

The total world steel production in 2019 amounted to 1869 million tons, of which the steel production in the electric arc furnace amounted to more than 30% of the world steel production [1-3]. Steel production from secondary raw materials, so-called scrap iron, is performed in an electric arc furnace (EAF) at a temperature of 1600°C, where during the melting of the batch the elements from the iron melt evaporate, which leads to the formation of the main intermediate of the process - electric arc furnace dust (EAF dust) [3-7]. In general, about 10-20 kg of EAF dust is generated during the production of 1 ton of crude steel [5, 8-10]. Electric arc furnace dust contains significant amounts of zinc and solid iron oxides, as well as variable amounts of Pb, Ca, Mn, Ni, Cu, Cd, Mg, Si, Cr, F, Cl, etc. [1, 8-10]. The Zn content in EAF dust varies between 2 and 40% [2, 5, 6, 8-10]. Due to the fact that EAF dust is formed under oxidation conditions, most metals are present in the form of metal oxides. Zinc occurs in the form of ZnO and ZnFe₂O₄, while iron mainly occurs in the oxide form as Fe₃O₄ and Fe₂O₃ [3, 5, 8, 9]. The presence of heavy metals such as Pb and Cd in EAF dust can pose a threat to the environment and human health, and for this reason EAF dust is considered officially hazardous industrial solid waste in many countries [4, 5, 6, 9, 8, 10, 11].

In this paper, a laboratory experimental study of hydrometallurgical treatment of EAF dust originating from a steel plant in the Republic of Serbia was performed. Chemical characterization of EAF dust, laboratory experimental tests of EAF dust water leaching process

in order to remove chlorides and other water-soluble compounds, as well as tests of acid leaching process of solid residue obtained after water leaching in order to separate zinc were performed.

2. EXPERIMENTAL

Chemical characterization was performed on a reference sample of EAF dust by the following methods: Atomic Absorption Spectrophotometry (AAS), Volumetry (V), Inductively Coupled Plasma Atomic Emission Spectroscopy (ICP-AES), Spectrophotometry (SF), Carbon/Sulfur Analyzer (ACS).

Laboratory experimental investigations of hydrometallurgical treatment of EAF dust include water leaching and acid leaching processes. The parameters of the water and acid leaching processes at ambient temperature were investigated. All leaching experiments were performed on an initial EAF dust sample in an amount of 100 g, in a glass reactor with volume of 1 L, equipped with a stirrer with speed control and a device for automatic temperature control. For acid leaching experiments with the addition of oxidants, O₂ from a pressurized bottle was used.

3. RESULTS AND DISCUSSION

The chemical composition of the initial EAF dust sample is presented in Table 1.

Table 1 - Chemical composition of the initial EAF dust sample

Element	Zn	Fe	Mn	Cu	Pb	Co	K	Ni	Cr	Ca	Cd
Content (%)	32.44	18.92	1.81	0.19	1.39	0.0017	0.87	0.036	0.25	3.85	0.04
Element	Cl	Mo	S	P	As	Sb	Sn	Al	Si	Na	Mg
Content (%)	2.85	<0.005	0.51	0.15	0.0041	0.022	0.037	0.73	1.0	1.28	0.93

3.1. Water leaching of EAF dust

The following parameters of the EAF dust water leaching process were investigated: pulp density 5-20%, ambient temperature-80°C and pH correction to <11. Process parameters such as the leaching process duration of 60 min and the mixing speed of 750 rpm remain constant in all experiments.

The 1st stage of hydrometallurgical treatment of EAF dust was performed in order to remove chlorides and other water-soluble compounds from EAF dust, such as Ca, Mg, K, and Na. The effects of water leaching EAF dust are a reduction in the consumption of sulfuric acid and chlorine ions in the second stage of leaching. The test results of the water leaching process confirm the removal of chloride from EAF dust, as well as other water-soluble elements. The leaching rates of chlorides and soluble compounds from EAF dust in water are shown in Figure 1 and amount to 80.84% Cl, 60.63% K, 52.95% Na, 18.23% Ca, 0.14% Zn and <0.0006% Pb.

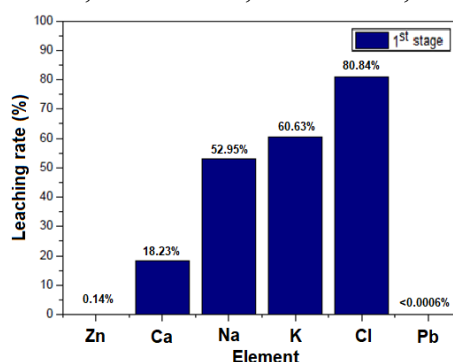


Figure 1 - Leaching rates of chlorides and water-soluble compounds

In water leaching experiments without pH correction, the pH of the suspension is above 11 at the end of leaching, which causes an increase in the concentration of Pb and Zn in the pregnant leaching solution. In order to prevent leaching of Pb and Zn with water, the pH of the suspension was corrected to <11 by adding concentrated HNO₃. The mass of the solid residue after water leaching without heating is reduced by about 10% compared to the initial mass of the EAF dust sample. The same percentage of weight reduction was shown in the experiment performed at a temperature of 80°C, which means that the increased temperature is not necessary during water leaching process. Also, no significant influence of pulp density on the metal concentration in the solution after leaching was observed, so that the pulp density of 20% was taken as the optimal parameter.

3.2. Acid leaching of the solid residue

After the 1st stage of hydrometallurgical treatment of EAF dust, the obtained solid residue was leached in the 2nd stage with sulfuric acid at ambient temperature in order to leach ZnO from EAF dust and obtain a solution of ZnSO₄. The following process parameters were examined: H₂SO₄ concentration (0.25M, 0.5M, 0.75M, 1.0M and 1.5M), leaching process time (10 and 20 min), as well as oxidant addition (O₂), while a pulp density of 20% and a stirring speed of 750 rpm were constant.

Leaching rate of the tested elements depending on the concentration of H₂SO₄ without addition of oxidant is presented in Figure 2. From the obtained results it can be concluded that the leaching rate of Zn increases with increasing H₂SO₄ concentration for both tested leaching times (10 and 20 min). The highest Zn leaching rate of 71.63% was achieved by leaching with 1.5M H₂SO₄ over a time of 10 min. Leaching rate of Cu and Fe increases significantly at H₂SO₄ concentrations above 0.75M H₂SO₄. With increasing concentration of H₂SO₄, the leaching rate of Ca and Ni does not change significantly. Leaching rate of Cd leaching increases with increasing H₂SO₄ concentration from 0.25M to 0.75M. With a further increase in the concentration of H₂SO₄ from 0.75M to 1.5M, no significant change in the leaching rate of Cd was observed.

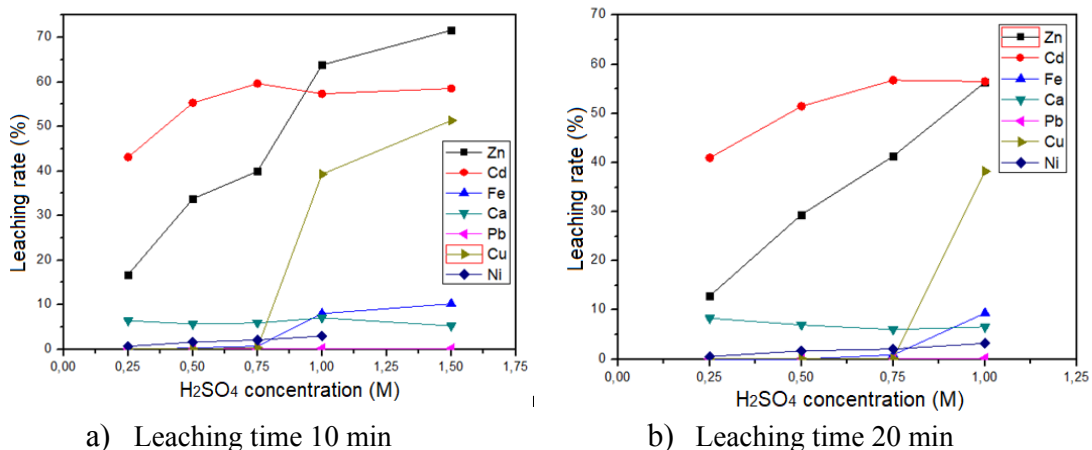


Figure 2 - Leaching rate depending on the concentration of H₂SO₄ at a leaching time of 10 min and 20 min (leaching reagent 0.25-1.5M H₂SO₄, pulp density 20%, mixing speed 750 rpm, ambient temperature, without oxidant addition)

Investigation results of the addition of O₂ influence as an oxidant on Zn leaching showed that the Zn leaching rate significantly increases with the addition of oxidant during the acid leaching process. The achieved Zn leaching rate with the addition of oxidant is 10% higher than the leaching rate without the addition of oxidant at the same tested process parameters (leaching with

1.5M H₂SO₄, pulp density of 20%, leaching time 10 min, mixing speed 750 rpm, ambient temperature) and amounts to 82.34%.

After acid leaching, the obtained solid residue showed the characteristics of non-hazardous waste based on TCLP and LP tests.

4. CONCLUSION

In order to separate Zn from EAF dust as a valuable component, hydrometallurgical treatment of EAF dust was investigated. The treatment consists of two stages: 1st stage of leaching with water was performed in order to remove water-soluble compounds, and 2nd rate of leaching with sulfuric acid in order to leach ZnO from EAF dust and obtain a solution of ZnSO₄. The achieved leaching rates of water-soluble compounds from EAF dust are 80.84% Cl, 60.63% K, 52.95% Na, and 18.23% Ca at the following optimal process parameters: pulp density 20%, ambient temperature, time 60 min, stirring speed 750 rpm and pH correction to pH <11.

The best results of acid leaching were achieved by leaching the solid residue obtained after water leaching EAF dust at the following parameters: 1.5M H₂SO₄ with the addition of O₂ as oxidant, pulp density 20%, leaching time 10 min, stirring speed 750 rpm at ambient temperature. Leaching rate of Zn at these leaching parameters is 82.34%. Apart from the economic one, the investigated treatment has also ecological significance because it transforms the starting material which represents hazardous industrial solid waste into non-hazardous waste, which can be disposed of at a non-hazardous waste landfill without risk to the environment.

ACKNOWLEDGEMENTS

This work was supported by the Ministry of Education, Science and Technological Development of the Republic of Serbia, Grant No. 451-03-9/2021-14/200052.

REFERENCES

- [1] V. Montenegro, S. Agatzini-Leonardou, P. Oustadakis and P. Tsakiridis, Waste Biomass Valorization, 7 (6) (2016) 1531–1548.
- [2] M. Čerňan, Z. Müller, J. Tlustý, V. Valouch, Int. J. Electr. Power Energy Syst. 129 (2021) 106831.
- [3] F. Kukurugya, T. Vindt, T. Havlík, Hydrometal. 154 (2015) 20–32.
- [4] W. J. Bruckarda, K. J. Daveya, T. Rodopouloa, J. T. Woodcocka, J. Italiano, Int. J. Miner. Process. 75 (2005) 1 – 20.
- [5] J. Wang, Y. Zhang, K. Cui, T. Fu, J. Gao, S. Hussain, T. S. AlGarni, J. Cleaner Prod. 298 (2021) 126788.
- [6] V. S. Silvaa, J. S. Silvaa, B. dos S. Costaa, C. Labesb, R. M. P. B. Oliveira, J. Mater. Res. Technol. 8(6) (2019) 5504–5514.
- [7] G. Laforest, J. Duchesne, J. Hazard. Mater. B135 (2006) 156–164.
- [8] P. K Hazaveh, S. Karimia, F. Rashchia, S. Sheibania, Ecotoxicol. Environ. Saf. 202 (2020) 110893
- [9] C. A. Pickles, Miner. Eng. 22 (2009) 977–985.
- [10] T. Havlika, M. Turzakovaa, S. Stopic, B. Friedrich, Hydrometal. 77 (2005) 41–50.
- [11] <https://www.scribd.com/doc/26038172/Evropski-katalog-otpada>

ISBN 978-86-6305-119-5